



# Primary interphase dendritic growth via unsteady-state horizontal solidification of an Al-Cu-Nb alloy

  <https://doi.org/10.56238/alookdevelopv1-173>

## Evaldo da Cruz Hoffmann

Materials Engineering Course, Federal Institute of Education, Science and Technology of Pará - IFPA  
E-mail: evaldohoffmannfaculdade@gmail.com

## Bruno Yuji Goto Feio

Materials Engineering Course, Federal Institute of Education, Science and Technology of Pará - IFPA  
E-mail: bruno.yuji@outlook.com

## Thiago Maués Oliveira Dillon

Graduate Program in Materials Federal Institute of Education, Science and Technology of Pará - IFPA  
E-mail: thiago.dillon@gmail.com

## Hugo André Magalhães de Azevedo

Graduate Program in Mechanical Engineering, Federal University of Pará - UFPA  
E-mail: hugoodeveza@gmail.com

## Fernando Sousa da Rocha

Graduate Program in Mechanical Engineering, Federal University of Pará - UFPA  
E-mail: nandosrocha12@gmail.com

## Otávio Fernandes Lima da Rocha

Professor, Materials Engineering Graduate Program, Federal Institute of Education, Science and Technology of Pará - IFPA, and Mechanical Engineering Graduate Program, Federal University of Pará - UFPA  
E-mail: otavio.rocha@ifpa.edu.br

## ABSTRACT

Aluminum and its alloys, compared to steel, have a higher strength/weight ratio, good electrical and thermal conductivity, and better corrosion resistance. Among the various aluminum alloys registered today, we can highlight those that make use of copper, the third most consumed metal in the world. In this context, niobium stands out, which plays an important role in the production of metallic alloys due to its high melting point, resistance to acid attack, and superconductivity at high temperatures. In recent decades, several studies have been carried out to establish the relationship between the thermal solidification parameters and typical as-cast structure in macrostructural and microstructural scales in aluminum alloys, aiming to optimize the properties of these alloys. In this sense, the main objective of this work was to investigate the effects of heat flow parameters, such as growth and cooling rates ( $V_L$  and  $T_R$ ), on primary interphase dendritic growth ( $\lambda_{1\alpha}$ ) in equiaxed dendrites in Al-3Cu-0.5Nb (wt.%) alloy (wt.%), which was horizontally solidified in a recent study. The  $\lambda_{1\alpha}$  variation with  $V_L$  and  $T_R$  has been characterized by mathematical equations given by the general expressions  $\lambda_{1\alpha} = \text{Constant} \cdot (V_L)^{-1.1}$  and  $\lambda_{1\alpha} = \text{Constant} \cdot (T_R)^{-0.55}$ , which represents the interphase dendritic growth laws, where the exponents -0.55 and -1.1 are in absolute agreement with the primary spacing growth laws in columnar dendrites.

**Keywords:** Unsteady-state horizontal solidification, Thermal parameters, Primary interphase dendritic growth, Al-Cu-Nb alloys.

## 1 INTRODUCTION

It is known that Brazil stands out for its significant participation in the world production of aluminum and its alloys. It is the fifteenth-largest producer of primary aluminum and the fourth-largest producer of bauxite, with the state of Pará representing about 89.5% of this product [1]. China and Australia are also countries that stand out. In the Brazilian domestic market, aluminum is mainly used by the transport industries, such as automobile and aeronautics, and packaging, which are followed by the electricity, civil construction, consumer goods, and machinery segments, among others [1-3].

Another metal, niobium (Nb), on which Brazil practically has a monopoly, which still does not have perfect substitutes. Almost all world reserves of this metal, 98.2%, are in Brazil, which is also the largest producer of the element, representing more than 90% of the world's total, according to data from the National Mining Association [4]. The main application of niobium is in the formation of micro-alloyed steels, finding applications in civil construction, mechanical industry, aerospace, naval, automotive, oil and gas pipes, and oil platforms, among others, and it is evident, therefore, how significant it would be for the country to discover new applications that could increase the demand for the metal and increase its added value. Hence, the importance of scientific research for the development of new materials with potential possibilities for future applications in the transformation industries is urgent [4].

Relative to steel, aluminum alloys have a higher strength-to-weight ratio, good electrical and thermal conductivity, and better corrosion resistance. Its disadvantages include a low mechanical strength, especially at high temperatures, as well as a low tensile strength, ranging between 90 and 180 MPa, which ends up restricting its application as a structural material and generally limits it to components of thermal and electrical systems, where it is possible to benefit from its high conductivities without a great requirement about mechanical properties [5-7]. Therefore, it is necessary to improve some of its properties to have better performance and applicability in the industry [6-13]

Among the hundreds of registered aluminum alloys, those of the Al-Cu and Al-Si systems stand out, which are the most used by the automotive and aerospace industries. In the case of Al-Cu alloys, those of greatest industrial interest are the thermally treated ones, in which Cu contents are in the range of 2 to 5% [9,10]. These alloys are known as dura-aluminum and belong to the 2XXX (wrought) and 2XX.X (cast) series in the Aluminum Association classification [2] and are among the oldest aluminum-based alloys. They are widely used in the manufacture of components in the aeronautical and automotive industries, such as aircraft leading edges, structural parts, cylinders, pistons, and engine blocks [9,10,12].

Studies have been carried out with alloys of the duralumin series, which are binary, ternary, or quaternary multicomponent alloys, which have in their composition copper with the addition of silicon, magnesium, titanium, nickel, and others that provide aluminum with excellent mechanical resistance at high temperatures, especially with heat-treated alloys. Niobium, for example, has been one of those elements that, in recent studies, has been investigated as an added element in Al alloys [14-22].

Considering the aforementioned highlights of aluminum-based alloys and observing the continuous development of research related to niobium and its importance for Brazil, as well as due to the scarcity of relevant information on the effects of Nb composition, as well as of solidification path of these alloys, this work as main goal to investigate the effects of thermal solidification parameters,

such as the growth and cooling rates ( $V_L$  and  $T_R$ ) on the primary dendritic microstructural scale length of the Al-3Cu-0.5Nb alloy (wt.%).


## 2 EXPERIMENTAL PROCEDURE

The studied alloy, the horizontal solidification experiment, and thermal analyzes to determine the desired thermal parameters ( $V_L$  and  $T_R$ ) were obtained in works recently published by our research group [15,16]. During the preparation of the alloy, because Nb has a very high melting point ( $\sim 2468$  °C), which is much higher than that of the other constituent elements of the alloy, Al and Cu, its insertion into the liquid metal occurred last, given the diffusion mechanism under high temperatures for its integration as the second solute in the liquid matrix of the solvent (Al) [16].

The thermal data acquisition system used during the solidification process consisted of a temperature recorder (FieldLogger) connected to a computer and data recording software that receives these values and converts them into a notepad in the form of ordered pairs ( $T$ ,  $t$ ). This notepad was imported into another data processing software (OriginPro), where the thermal solidification profiles were plotted, and from the same, the experimental  $V_L$  and  $T_R$  values were determined [6-10,15,16,23].

Cross-sectional as-cast samples from the solidified ingot resulting from the work of [15,16] were prepared, considering positions from the heat transfer surface of the ingot mold of the water-cooled solidification device, aiming to evaluate the effects of  $V_L$  and  $T_R$  on the evolution of the dendritic microstructure, which was quantified by the interphase spacing of the primary dendritic arms ( $\lambda_{1\alpha}$ ) of the Al-rich phase. The measurement of  $\lambda_{1\alpha}$ , shown schematically in Figure 1, according to References [24,25], was based on the neighborhood criterion. That is, the primary spacing value is equal to the average distance between the centers of the primary dendritic arms. This method is known as the "triangle method". The assumed  $\lambda_{1\alpha}$  values were the averages among 20 measurements performed for each sample from the cooled mold plate.


Figure 1. The technique used to measure interphase spacing ( $(\lambda_{1\alpha})$ )

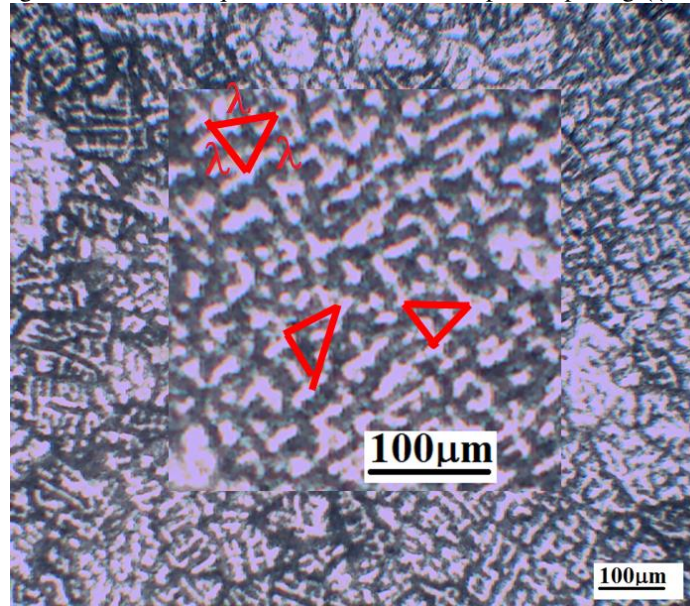

### 3 RESULTS AND DISCUSSIONS


The effects of the cooling system promoted by the horizontal solidification device were evaluated on the evolution of the dendritic microstructure along the length of the as-cast ingot, as shown in Figure 2. As can be seen, the macrostructure consisted of fine equiaxed grains along the length of the ingot, and finer and coarser dendritic microstructures were obtained for positions closer and farther from the heat transfer interface (cooling base) as growth and cooling rates became higher and lower, respectively.

Figure 2. Typical solidification structures of Al-3Cu-0.5Nb alloy (wt.%) solidification in scales: (a) macrostructural, obtained by Dillon [15,16], and (b) microstructural showing the primary interphase dendrites.

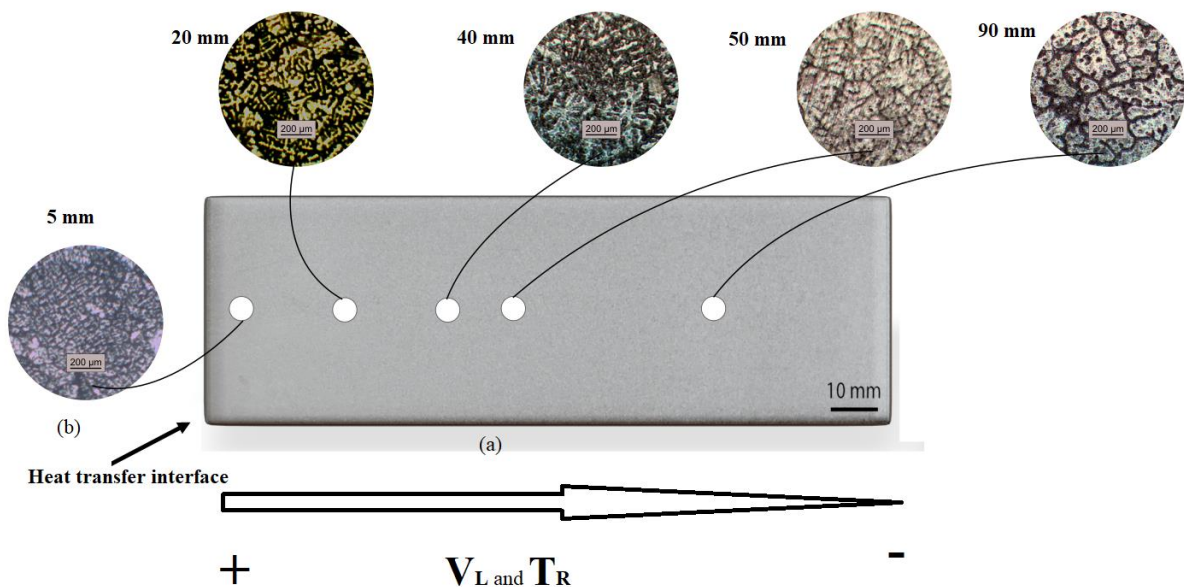

Dillon et al. [15,16] carried out thermal analyzes resulting from the horizontal solidification process under the same conditions assumed in this work and proposed mathematical expressions to correlate the thermal solidification parameters ( $V_L$  and  $T_R$ ) as a function of the position in the as-cast ingot, given by  $V_L=2.17(P)^{-0.3}$  and  $T_R=82.8(P)^{0.7}$ . It could be noticed that the  $V_L$  and  $T_R$  values gradually decrease with the advance of solidification due to the increasing formation of the solid layer that promotes resistance by thermal conduction, thus influencing the dendritic microstructures shown in Figure 2b. The interphase spacing measurements ( $\lambda_{1\alpha}$ ), as shown in Figure 2, as well as the aforementioned functions  $V_L=f(P)$  and  $T_R=f(P)$ , were used in this study to establish a relationship of  $\lambda_{1\alpha}$  as a function of the position in as-cast ingot ( $P$ ),  $V_L$  and  $T_R$ , whose results are shown in Figure 3. As noted, equiaxed primary dendrite growth laws represented by power-type mathematical expressions were proposed, which allowed experimentally predicting the dependence of interphase dendritic spacing as a function of the thermal solidification parameters. It can be highlighted in this work that the exponents obtained equal to -1.1 and -0.55 agree with the theoretical and experimental growth laws proposed in the literature for primary dendritic spacing measured in columnar dendrites [6-10,24,25], confirmed by the comparative analysis carried out with the study by Barros et al. [9,10] for a horizontally solidified Al-3wt.%Cu alloy, as shown in Figures 3b and 3c.

Figure 3. Primary dendritic interphase spacings as a function of (a) Position in the as-cast ingot, (b) and (c) growth and cooling rates.

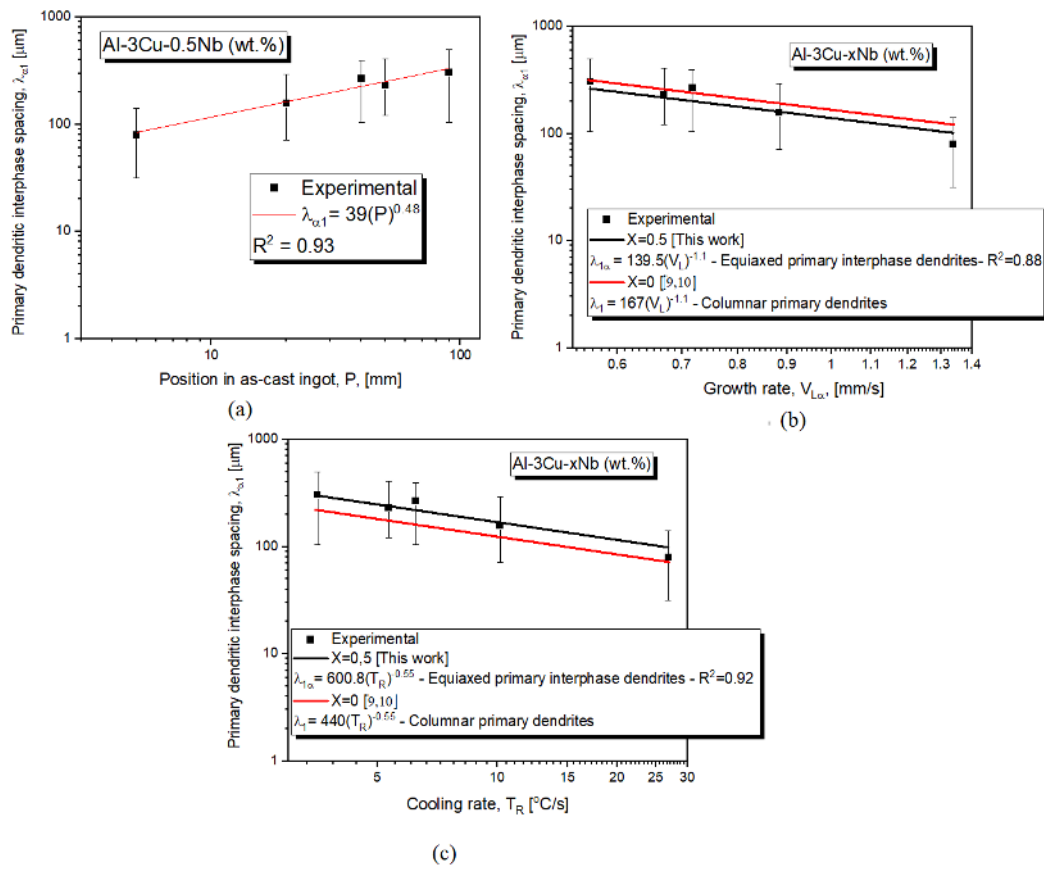

## 4 CONCLUSIONS

In this study, the effects of thermal solidification parameters were investigated on primary dendritic interphase spacings during horizontal solidification of the Al-3Cu-0.5Nb alloy (wt.%); the following conclusions can be drawn:

“The dependence of primary interphase dendritic arm spacings on thermal parameters  $V_L$  and  $T_R$  for the Al-3wt.%Cu-0.5wt.%Nb alloy was investigated, and the relationships among them have been obtained. Mathematical expressions given by  $\lambda_{1\alpha}=139.5(V_L)^{-1.1}$  and  $\lambda_{1\alpha}=600.8(T_R)^{-0.55}$  have been proposed to experimentally predict the growth laws of  $\lambda_{1\alpha}$  as a function of  $V_L$  and  $T_R$ . It was observed that the exponents -1.1 and -0.55 obtained, suggested for columnar dendrites, can also be applied to characterize the experimental variation of  $\lambda_{1\alpha}$  with  $V_L$  and  $T_R$  values for equiaxed interphase dendrites, respectively”.

## ACKNOWLEDGMENTS

The authors acknowledge the financial support provided by IFPA-Federal Institute of Education, Science, and Technology of Pará (EDITAL n. 05/2022 – PIBICTI/PROPPG/IFPA/CNPq), Postgraduate Program in Materials Engineering (PPGEMat/IFPA), UFPA-Federal University of Pará, and CNPq-National Council for Scientific and Technological Development (Grant 304924/2020-2), CAPES - Coordination of Superior Level Staff Improvement, Brazil.

## REFERENCES

1. ABAL - Associação Brasileira de Alumínio. Perfil da Indústria Brasileira de Alumínio. 2020. Disponível em: <<http://abal.org.br/estatisticas/nacionais/perfil-da-industria/>>. Acesso em: 01 jun. 2023.
2. ALUMINUM ASSOCIATION. Aluminum standards and data. The Aluminum Association, Inc., 2013.
3. ASM HANDBOOK COMMITTEE (Org.). Properties and Selection: Nonferrous Alloys and Special-Purpose Materials. Materials park, Ohio: ASM International, 1990.
4. ANM - Associação Nacional de Mineração. Sumário Mineral 2017. 2017. Disponível em: <[https://www.gov.br/anm/pt-br/centrais-de-conteudo/publicacoes/serie-estatisticas-e-economia-mineral/sumario-mineral/sumariomineral\\_2017/](https://www.gov.br/anm/pt-br/centrais-de-conteudo/publicacoes/serie-estatisticas-e-economia-mineral/sumario-mineral/sumariomineral_2017/)>. Acesso em: 01 jun. 2023.
5. RODRIGUES, Jean Robert Pereira. Efeito da composição nos parâmetros térmicos e estruturais de ligas Al-Mg solidificadas unidirecionalmente. 161p. Tese (Doutorado em Engenharia Mecânica) – Faculdade de Engenharia Mecânica, Universidade Estadual de Campinas, Campinas, SP, 2007.
6. AZEVEDO, H. M. et al. Microstructural Development of an AlNiBi Alloy and Influence of the Transient Horizontal Solidification Parameters on Microhardness. Metallurgical and Materials Transactions A, v. 49, n. 10, p. 4722–4734, out. 2018. DOI: <https://doi.org/10.1007/s11661-018-4747-4>. Disponível em: <https://link.springer.com/article/10.1007/s11661-018-4747-4>. Acesso em: 01 jun. 2023.
7. BARBOSA, C. R. et al. Relationship Between Aluminum-Rich/Intermetallic Phases and Microhardness of a Horizontally Solidified AlSiMgFe Alloy. Materials Research, v. 22, n. 1, out. 2018. DOI: <http://dx.doi.org/10.1590/1980-5373-mr-2018-0365>. Disponível em: [https://www.researchgate.net/publication/329174021\\_Relationship\\_Between\\_Aluminum-RichIntermetallic\\_Phases\\_and\\_Microhardness\\_of\\_a\\_Horizontally\\_Solidified\\_AlSiMgFe\\_Alloy](https://www.researchgate.net/publication/329174021_Relationship_Between_Aluminum-RichIntermetallic_Phases_and_Microhardness_of_a_Horizontally_Solidified_AlSiMgFe_Alloy). Acesso em: 01 jun. 2023.
8. BARBOSA, C. R. et al. Tailoring of Processing Parameters, Dendritic Microstructure, Si/Intermetallic Particles and Microhardness in As-cast and Heat-Treated Samples of Al7Si0.3Mg Alloy. Metals and Materials International, v. 26, p. 370–383, jun. 2019. DOI: <https://doi.org/10.1007/s12540-019-00334-y>. Disponível em: <https://link.springer.com/article/10.1007/s12540-019-00334-y#citeas>. Acesso em: 01 jun. 2023.
9. BARROS, A. S et al. Measurements of microhardness during transient horizontal directional solidification of Al-rich Al-Cu alloys: effect of thermal parameters, primary dendrite arm spacing and Al2Cu intermetallic phase. Metals and Materials International, v. 21, p. 429-439, 2015. DOI: <https://doi.org/10.1007/s12540-015-4499-2>. Disponível em: <https://link.springer.com/article/10.1007/s12540-015-4499-2>. Acesso em: 01 jun. 2023.
10. BARROS, André dos Santos. Solidificação horizontal das ligas Al-3%Cu e Al-3%Cu-0,5%Mg: estrutura dendrítica, microdureza, resistência à corrosão e aplicação do tratamento térmico T6 na liga ternária. Dissertação (Mestrado em Engenharia Mecânica) – Faculdade de Engenharia Mecânica, Universidade Federal do Pará, Belém, Pará, 2018.

11. ÇADIRLI, E. Effect of Solidification Parameters on Mechanical Properties of Directionally Solidified Al-Rich Al-Cu Alloys. *Metals Materials International*, v. 19, p. 411-422, 2013. DOI: <https://doi.org/10.1007/s12540-013-3006-x> Disponível em: <https://link.springer.com/article/10.1007/s12540-013-3006-x>. Acesso em: 01 jun. 2023.
12. LI, S. et al. Influence of Mg Contents on Aging Precipitation Behavior of Al–3.5Cu–xMg Alloy. *Acta Metallurgica Sinica*, v. 27, p. 107- 114, fev. 2014. DOI: <https://doi.org/10.1007/s40195-014-0033-7>. Disponível em: <https://link.springer.com/article/10.1007/s40195-014-0033-7>. Acesso em: 01 jun. 2023.
13. GARCIA, A. *Solidificação: fundamentos e aplicações*. Campinas: Editora da Unicamp, 2007.
14. COUTINHO, M. M. et al. Upward Unsteady-State Solidification of Dilute Al–Nb Alloys: Microstructure Characterization, Microhardness, Dynamic Modulus of Elasticity, Damping, and XRD Analyses. *Metals*, v. 9, n. 6, p. 713, jun. 2019. DOI: <https://doi.org/10.3390/met9060713> Disponível em: <https://www.mdpi.com/2075-4701/9/6/713>. Acesso em: 01 jun. 2023.
15. DILLON, Thiago Maues Oliveira. *Desenvolvimento e Caracterização Térmica, Microestrutural e Mecânica de uma Liga Al-3%Cu-0,5%Nb Solidificada Horizontalmente e Endurecida por Precipitação*. Dissertação (Mestrado em Engenharia de Materiais) – Instituto Federal do Pará, Belém, 2021.
16. DILLON, T. et al. Effects of Growth and Cooling Rates Via Horizontal Solidification of an AlCuNb Alloy: A Thermal, Microstructural and Mechanical Analysis. *Transactions of the Indian Institute of Metals*, v. 75, n. 6, p. 1429–1439, jan. 2022. DOI: <https://doi.org/10.1007/s12666-021-02501-5> Disponível em: <https://link.springer.com/article/10.1007/s12666-021-02501-5>. Acesso em: 01 jun. 2023.
17. JESUS, Emerson de Sousa de. *Influência da Granulometria de Nióbio e Tempo de Moagem na Obtenção da Liga Al1,2%Nb via Metalurgia do Pó*. Dissertação (Mestrado em Ciências Mecânicas) – Faculdade de Tecnologia, Universidade de Brasília, Brasília, 2018.
18. MAHDOUK, K.; GACHON, J-C.; BOIRDEN, L. Enthalpies of formation of the Al–Nb intermetallic compounds. *Journal of Alloys and Compounds*, v. 268, n. 1, p. 118–121, fev. 1998. DOI: [https://doi.org/10.1016/S0925-8388\(97\)00554-9](https://doi.org/10.1016/S0925-8388(97)00554-9). Disponível em: <https://www.sciencedirect.com/science/article/abs/pii/S0925838897005549>. Acesso em: 01 jun. 2023.
19. MUNITZ, A.; GOKHALE, A. B.; ABBASCHIAN, R. The effect of supercooling on the microstructure of Al-Nb alloys. *Journal of Materials Science*, v. 35, n. 9, p. 2263–2271, mai. 2000. DOI: <https://doi.org/10.1023/A:1004783011253>. Disponível em: <https://link.springer.com/article/10.1023/A:1004783011253>. Acesso em: 01 jun. 2023.
20. NANDI, P. et al. Solid state synthesis of Al-based amorphous and nanocrystalline Al–Cu–Nb alloys. *Materials Science and Engineering: A*, v. 359, n. 1–2, p. 11–17, jun. 2003. DOI: [https://doi.org/10.1016/S0921-5093\(03\)00338-1](https://doi.org/10.1016/S0921-5093(03)00338-1). Disponível em: <https://www.sciencedirect.com/science/article/abs/pii/S0921509303003381?via%3Dihub>. Acesso em: 01 jun. 2023.
21. NOVAKOVIC, R. Thermodynamics, surface properties and microscopic functions of liquid Al–Nb and Nb–Ti alloys. *Journal of Non-Crystalline Solids*, v. 356, n. 31, p. 1593–1598, abr. 2010.

DOI: <https://doi.org/10.1016/j.jnoncrysol.2010.05.055>. Disponível em:  
<https://www.sciencedirect.com/science/article/abs/pii/S0022309310002942?via%3Dihub>. Acesso em: 01 jun. 2023.

22. SOUSA, Thiago Primo. Evolução da microestrutura bruta de fusão de ligas Al-Cu-Nb solidificadas unidirecionalmente. Dissertação (Mestrado em Integridade de Materiais da Engenharia) – Faculdade UnB Gama, Universidade de Brasília, DF, 2019.

23. LIMA, J. O. et al. Microstructural evolution during unsteady-state horizontal solidification of Al-Si-Mg (356) alloy. *Transactions of Nonferrous Metals Society of China*, v. 28, n. 6, p. 1073–1083, jun. 2018. DOI: [https://doi.org/10.1016/S1003-6326\(18\)64751-X](https://doi.org/10.1016/S1003-6326(18)64751-X). Disponível em: <https://www.sciencedirect.com/science/article/abs/pii/S100363261864751X?via%3Dihub>. Acesso em: 01 jun. 2023.

24. MCCARTNEY, D. G.; HUNT, J. D. Measurements of cell and primary dendrite arm spacings in directionally solidified aluminium alloys. *Acta Metallurgica*, v. 29, n. 11, p. 1851–1863, nov. 1981. DOI: [https://doi.org/10.1016/0001-6160\(81\)90111-5](https://doi.org/10.1016/0001-6160(81)90111-5). Disponível em: <https://www.sciencedirect.com/science/article/abs/pii/0001616081901115?via%3Dihub>. Acesso em: 01 jun. 2023.

25. GÜNDÜZ, M.; ÇADIRLI, E. Directional solidification of aluminium-copper alloys. *Materials Science and Engineering A*, v. 327, n. 2, p. 167-185, fev. 2002. DOI: [https://doi.org/10.1016/S0921-5093\(01\)01649-5](https://doi.org/10.1016/S0921-5093(01)01649-5). Disponível em: <https://www.sciencedirect.com/science/article/abs/pii/S0921509301016495>. Acesso em: 01 jun. 2023.